

III-V Growth on Silicon Toward a Multijunction Cell

J. Geisz, J. Olson, W. McMahon, D. Friedman,
A. Kibbler, C. Kramer, M. Young, A. Duda, S. Ward,
A. Ptak, S. Kurtz, M. Wanlass, P. Ahrenkiel,
C.S. Jiang, H. Moutinho, A. Norman, K. Jones,
M. Romero, and B. Reedy

*Presented at the 2005 DOE Solar Energy Technologies
Program Review Meeting
November 7–10, 2005
Denver, Colorado*

Conference Paper
NREL/CP-520-38996
November 2005

NREL is operated by Midwest Research Institute • Battelle Contract No. DE-AC36-99-GO10337



NOTICE

The submitted manuscript has been offered by an employee of the Midwest Research Institute (MRI), a contractor of the US Government under Contract No. DE-AC36-99GO10337. Accordingly, the US Government and MRI retain a nonexclusive royalty-free license to publish or reproduce the published form of this contribution, or allow others to do so, for US Government purposes.

This report was prepared as an account of work sponsored by an agency of the United States government. Neither the United States government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States government or any agency thereof.

Available electronically at <http://www.osti.gov/bridge>

Available for a processing fee to U.S. Department of Energy
and its contractors, in paper, from:

U.S. Department of Energy
Office of Scientific and Technical Information
P.O. Box 62
Oak Ridge, TN 37831-0062
phone: 865.576.8401
fax: 865.576.5728
email: <mailto:reports@adonis.osti.gov>

Available for sale to the public, in paper, from:

U.S. Department of Commerce
National Technical Information Service
5285 Port Royal Road
Springfield, VA 22161
phone: 800.553.6847
fax: 703.605.6900
email: orders@ntis.fedworld.gov
online ordering: <http://www.ntis.gov/ordering.htm>



Printed on paper containing at least 50% wastepaper, including 20% postconsumer waste

III-V Growth on Silicon Toward a Multi-Junction Cell

John Geisz, Jerry Olson, William McMahon, Daniel Friedman, Alan Kibbler, Charlene Kramer, Michelle Young, Anna Duda, Scott Ward, Aaron Ptak, Sarah Kurtz, Mark Wanlass, Phil Ahrenkiel, Chun Sheng Jiang, Helio Moutinho, Andrew Norman, Kim Jones, Manuel Romero, and Bob Reedy
National Renewable Energy Laboratory, Golden, Colorado, john_geisz@nrel.gov

ABSTRACT

A III-V on Si multijunction solar cell promises high efficiency at relatively low cost. The challenges to epitaxial growth of high-quality III-Vs on Si, though, are extensive. Lattice-matched (LM) dilute-nitride GaNPAs solar cells have been grown on Si, but their performance is limited by defects related to the nitrogen. Advances in the growth of lattice-mismatched (LMM) materials make more traditional III-Vs, such as GaInP and GaAsP, very attractive for use in multijunction solar cells on silicon.

1. Objectives

Today's fast-growing photovoltaic industry relies on silicon. Although the efficiencies of silicon modules have slowly increased, a two-junction cell on silicon has the potential for a dramatic (>10% absolute) efficiency boost. The purpose of this project is to explore the potential for low-cost, high-efficiency III-V-on-silicon solar cells.

2. Technical Approach

2.1 Nucleation of GaP Growth on Si

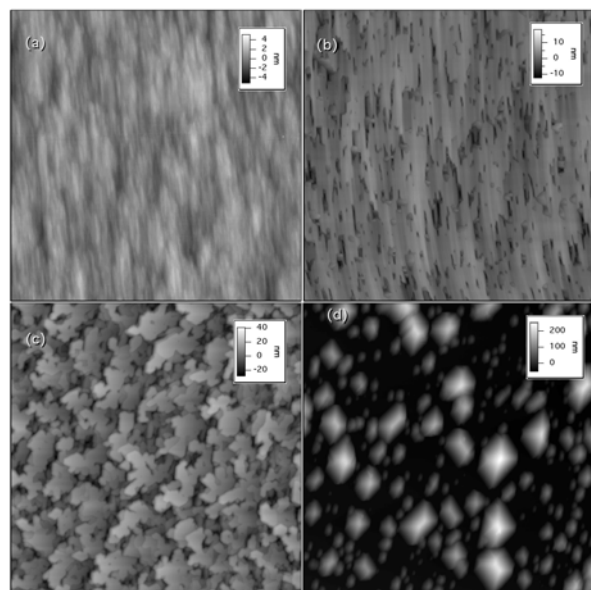


Fig. 1. AFM images of nominally 20-40nm GaP layer grown on Si. (a) PC197:APD-free [0.8nm RMS], (b) PC195:smooth, but some APDs [2.3nm RMS], (c) MG024:step-bunched terrace growth [7.9nm RMS], (d) MG025:island growth [52nm RMS]. All images are 5 x 5 μm and roughness is indicated in brackets.

The growth of an initial layer of smooth single-domain III-V layer on Si is an important step to achieve high-quality III-V materials grown on Si. We have studied a wide range of growth parameters to optimize this step. Atomic force microscopy (AFM), x-ray diffraction (XRD), transmission electron microscopy (TEM), and spectroscopic ellipsometry (SE) are used to measure and characterize these thin layers of GaP on Si.

2.2 Low dislocation density GaAsP and GaInP

LM dilute-nitride GaNPAs materials grown on Si^{1,2} or GaP³ have short diffusion lengths that limit the performance of such junctions. This is due to nitrogen related defects. GaAsP and GaInP materials are LMM with Si, but do not possess the detrimental nitrogen-related defect. Step graded buffer layers are grown to relieve the strain inherent to LMM heteroepitaxial growth. Growth conditions and layer structures are optimized to reduce the threading dislocations that are also detrimental to the diffusion lengths of these materials. The threading dislocations are imaged using spectral cathodoluminescence (CL) and TEM, and the resulting electrical properties are characterized with quantum efficiency (QE) of an electrochemical junction.

3. Results and Accomplishments

3.1 Nucleation of GaP growth on Si

We have employed state-of-the-art analytical techniques to understand the surface of the silicon and subsequent nucleation of GaP within a metal-organic chemical vapor deposition (MOCVD) reactor.^{4,5} We find that by growing on silicon substrates miscut 2° from (001) toward (111), we can achieve antiphase domain (APD)-free layers of GaP with extremely low roughness. Figure 1 shows AFM images of various GaP-on-Si layers. Oxide-free Si surfaces at growth temperature are required for APD-free growth. These can be achieved by desorbing the oxide at >1000°C under H₂ or in-situ etching with AsH₃ pretreatment at <800°C. Extremely high PH₃/Ga ratios are required during the initial nucleation growth. The temperature and pressure during growth are also key parameters. APD densities increase with reactor pressure making it very difficult to grow completely APD-free GaP-on-Si in our atmospheric-pressure reactor.

The high crystalline quality and low interface roughness of these GaP-on-Si layers have been

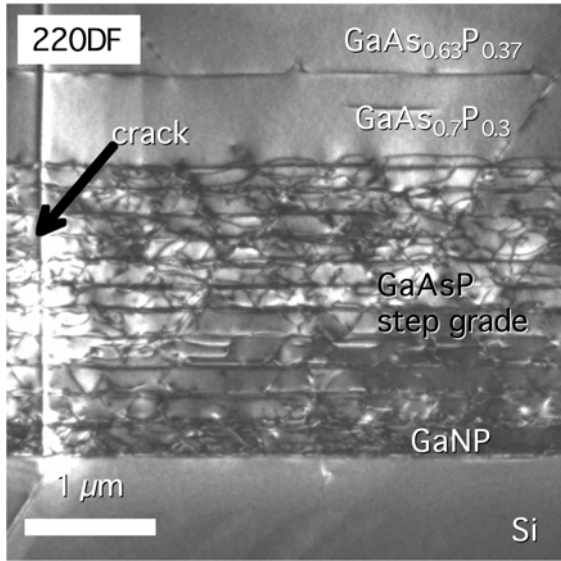


Fig. 2. Cross-sectional TEM of LMM GaAsP-on-Si graded structure (MF815).

demonstrated by nearly perfect dynamical fits to XRD measurements.

3.2 Low dislocation density GaAsP and GaInP

The dislocation density (DD) in thick layers of LMM GaAsP and GaInP is reduced by step graded buffer layers. Figure 2 shows TEM of a step-graded structure. Nearly LM GaNP layers are also used to achieve small steps in the mismatch of the grade. GaInP compositions are much easier to control, but GaAsP grades offer smoother morphology. The composition and strain state of the layers in these complex structures can be analyzed ex-situ using XRD reciprocal space maps as shown in Fig. 3. The management of strain during growth is difficult to deduce as a significant difference in thermal expansion between III-V materials and Si results in large changes during cool-down. Cracking of the

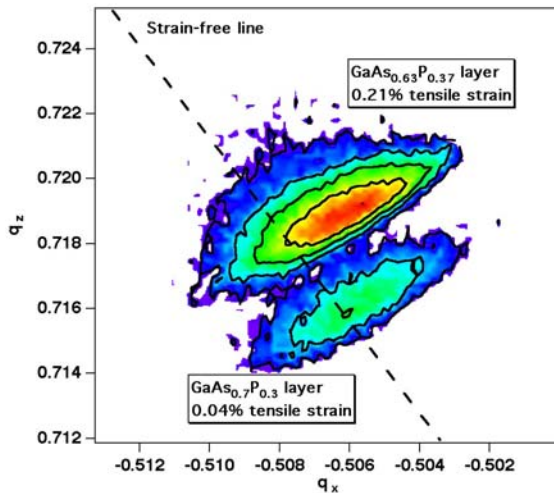


Fig. 3. X-ray diffraction reciprocal space map of the top layers of the LMM structure shown in Fig. 2. Grazing incidence 224 reflection.

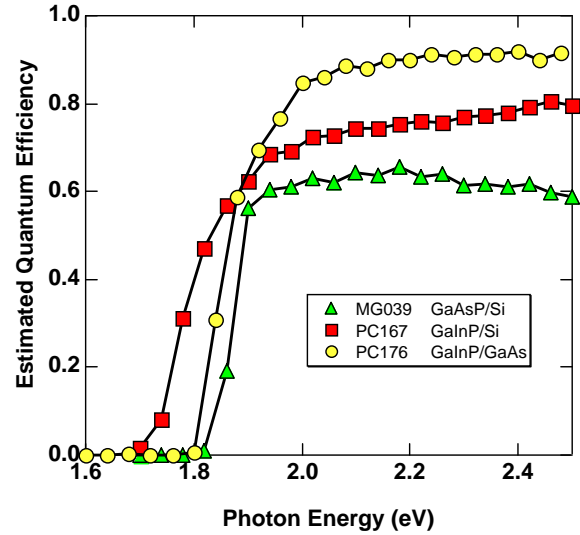


Fig. 4. Electrochemical QE of LMM III-V grown on Si compared with GaInP grown on GaAs.

structures due to large tensile strains during cool-down can be avoided by maintaining a residual compressive strain during growth. CL images reveal threading dislocation densities of about $8 \times 10^7 \text{ cm}^{-2}$ for unoptimized step-graded structures on Si. The electrochemical QE of step-graded GaAsP and GaInP structures in Fig. 4 show estimated quantum efficiencies approaching those of high quality GaInP grown on GaAs. The electrochemical QEs for these LMM materials on Si need to be confirmed in solid-state solar cells.

4. Conclusions

We have demonstrated nucleation of thin layers of high quality GaP on silicon. Subsequent growth of graded layers to relieve strain in LMM III-V materials has resulted in III-V layers with dislocation densities in the mid 10^7 cm^{-2} . Further reduction in the dislocation density should make possible high-efficiency III-V on silicon multijunction solar cells.

ACKNOWLEDGEMENTS

The work was performed under DOE contract DE-AC36-99-GO10337.

REFERENCES

1. J. F. Geisz, J. M. Olson, D. J. Friedman, et al., in *Proceedings of the 31st IEEE Photovoltaic Specialists Conference* (IEEE, Orlando, Florida, 2005), p. 695.
2. J. F. Geisz, J. M. Olson, and D. J. Friedman, in *19th European PV Solar Energy Conference and Exhibition*, Paris, 2004).
3. J. F. Geisz and D. J. Friedman, in *29th IEEE Photovoltaic Specialists Conference* (IEEE, New Orleans, 2002), p. 864.
4. J. F. Geisz, J. M. Olson, W. E. McMahon, et al., in *Material Research Society*, edited by D. J. Friedman, M. O. Manasreh, I. A. Buyanova, A. Munkholm and F. D. Auret (MRS, Boston, MA, 2003), Vol. 799, p. 27.
5. T. Hannappel, W. E. McMahon, and J. M. Olson, *J Crystal Growth* **272**, 24 (2004).

REPORT DOCUMENTATION PAGE*Form Approved*
OMB No. 0704-0188

The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to Department of Defense, Executive Services and Communications Directorate (0704-0188). Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.

PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ORGANIZATION.

1. REPORT DATE (DD-MM-YYYY) November 2005			2. REPORT TYPE Conference Paper		3. DATES COVERED (From - To)	
4. TITLE AND SUBTITLE III-V Growth on Silicon Toward a Multijunction Cell					5a. CONTRACT NUMBER DE-AC36-99-GO10337	
					5b. GRANT NUMBER	
					5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S) J. Geisz, J. Olson, W. McMahon, D. Friedman, A. Kibbler, C. Kramer, M. Young, A. Duda, S. Ward, A. Ptak, S. Kurtz, M. Wanlass, P. Ahrenkiel, C.S. Jiang, H. Moutinho, A. Norman, K. Jones, M. Romero, and B. Reedy					5d. PROJECT NUMBER NREL/CP-520-38996	
					5e. TASK NUMBER PVA6.4401	
					5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) National Renewable Energy Laboratory 1617 Cole Blvd. Golden, CO 80401-3393					8. PERFORMING ORGANIZATION REPORT NUMBER NREL/CP-520-38996	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)					10. SPONSOR/MONITOR'S ACRONYM(S) NREL	
					11. SPONSORING/MONITORING AGENCY REPORT NUMBER	
12. DISTRIBUTION AVAILABILITY STATEMENT National Technical Information Service U.S. Department of Commerce 5285 Port Royal Road Springfield, VA 22161						
13. SUPPLEMENTARY NOTES						
14. ABSTRACT (Maximum 200 Words) A III-V on Si multijunction solar cell promises high efficiency at relatively low cost. The challenges to epitaxial growth of high-quality III-Vs on Si, though, are extensive. Lattice-matched (LM) dilute-nitride GaNPAs solar cells have been grown on Si, but their performance is limited by defects related to the nitrogen. Advances in the growth of lattice-mismatched (LMM) materials make more traditional III-Vs, such as GaInP and GaAsP, very attractive for use in multijunction solar cells on silicon.						
15. SUBJECT TERMS Photovoltaics; solar; silicon; multi-junction cell; PV; NREL						
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT UL	18. NUMBER OF PAGES	19a. NAME OF RESPONSIBLE PERSON	
a. REPORT Unclassified	b. ABSTRACT Unclassified	c. THIS PAGE Unclassified			19b. TELEPHONE NUMBER (Include area code)	